

# Synthesis of Carbon Nanotubes Using Aliphatic Alcohols as a Carbon Source

Muhammed GJ<sup>1</sup> and Hussein F<sup>2\*</sup>

<sup>1</sup>Chemistry Department, College of Science, University of Babylon, Hilla, Iraq

<sup>2</sup>College Pharmacy, University of Babylon, Hilla, Iraq

## Introduction

Carbon nanotubes (CNTs) are graphite layers have hexagonal carbon rings rolled into cylinders which are discovered first in 1991 [1,2]. According to their unique properties of carbon nanotubes (CNTs) which coming from their atomic structure and size therefore CNTs take wide concerns in technology and science and wide range of application which CNTs entering in it such as electrodes, hydrogen storage and sensors [3,4]. CNTs have different structures and diameters which classified into three types such as: single-walled carbon nanotubes (SWNTs) and multi-walled carbon nanotubes (MWNTs) in addition to few wall carbon nanotubes (FWNTs) [5,6].

Different Methods are used for the synthesis of carbon nanotubes, such as, laser ablation [7], arc discharge [8] and chemical vapor deposition (CVD) [6,9]. Among different method were used for the synthesis CNTs, CVD is the preferred method because it is produce large quantity of CNTs and easy to control the properties of the product [10,11].

Carbon monoxide, hydrocarbons and alcohols such as ethanol, 1-propanol and 2-propanol are sources of carbon can be used in CVD method. Because of alcohols are makes less impurity and safe to treatment in the synthesis CNTs therefore consider the best carbon sources [6,12-14]. Ethanol can participate in the purification of the resulting CNTs when decomposition and produce OH radicals which act as etching agent by removing amorphous carbon during growth [15]. The process of synthesis CNTs can be done in two ways: the first without catalyst and the second by using a catalyst [16]. In this regard CVD method was used to synthesis CNTs by using alcohols such as ethanol, 1-propanol and 2-propanol as a source of carbon at temperature of 750°C.

Briefly, the process of synthesis CNTs includes heating the quartz tube furnace to the required temperature, and Fe/MgO was used as catalyst, then evaporating alcohol at a temperature below its boiling point by using a magnetic heater stirrer with the continuous flow of N<sub>2</sub> gas which is used as a carrier gas at rate equal to 100 cm<sup>3</sup>/min. The volume of alcohol which were used was 30 cm<sup>3</sup> and the process of evaporation took 1:30 hr. The heater of tube furnace was turn off when the evaporation process had finished with the continuous flow of N<sub>2</sub> gas until cooling the tube of the precipitation reaction. The purification process of the product which was divided into two types according to the type of synthesis CNTs such as with catalyst and without catalyst. The two products were purified by using the same ways which include: oxidation the remaining product by (30%) H<sub>2</sub>O<sub>2</sub> for 4 days at 70°C by using magnetic stirrer [6,17,18], the second type of product (with catalyst) were involved also reflux process of the product with 5 M nitric acid at 80°C for 7 hr.

The Characterization systems used to identify the types of CNTs with their percentage of purification were Raman spectroscopy and thermal gravimetric analysis (TGA). Raman spectroscopy was used to identification of CNTs and provide important information about CNTs such as microscopic structure, electron quantum confinement,

phonon and quality of tube [19]. Raman spectra as shown in Figure 1, contains three major peaks: D band at ~1352 cm<sup>-1</sup> which corresponding to amorphous carbon impurities and defects in the CNTs sample, the second peak G band was shifted at ~1599 cm<sup>-1</sup> because of high frequency in plan stretching of the C-C bonds, the last peak G' band at ~2550 cm<sup>-1</sup> is related to the process of double resonance [20]. The I<sub>D</sub>/I<sub>G</sub> ratio of the synthesized CNTs from 1-propanol with catalyst, ethanol with catalyst, 2-propanol with catalyst, ethanol without catalyst and 2-propanol without catalyst were 1.35, 1.8, 1.8, 2, 2.1 respectively. The increase the ratio of I<sub>D</sub>/I<sub>G</sub> which explain the increase number of defects on the sidewall of CNTs.

The TGA was used to evaluation the purities and qualities and to investigation of the presence of CNTs and to identify different types of carbon species [21]. According to the TGA analysis as show in Figure 2, it could be concluded that yield contains MWCNTs with less ratio of FWCNTs when was not used the catalyst, while the yield was mostly FWCNTs when the catalyst was used as shows in Table 1.

## References

1. Sinha N, John TWY (2005) Carbon nanotubes from biomedical applications IEEE Transactions on Nanobioscience 4: 180-195.
2. Iijima S (1991) Helical microtubules of graphite carbon. Nature 354: 56-58.
3. Chen JH, Li WZ, Wang DZ, Yang SX, Wen JG, et al. (2002) Electrochemical characterization of carbon nanotubes as electrode in electrochemical double-layer capacitors. Carbon 40: 1193-1197.
4. Dillon AC, Jones KM, Bekkedahl TA, Kiang CH, Bethune DS, et al. (1997) Storage of hydrogen in single-walled carbon nanotubes. Nature 386: 377-379.
5. Kenan S, Yiyang Z, Jiangsha M, Emily CG, Navid T, et al. (2013) Structural polymer-based carbon nanotube composite fibers: understanding the processing-structure-performance relationship. Materials 6: 2543-2577.
6. Jasim GM, Habeb FA, Hussein FH (2015) Synthesis of multi-walled carbon nanotube by using ethanol as a carbon source. Chem Sci J 6: e106.
7. Ren ZF, Huang ZP, Xu JW, Wang JH, Bush P, et al. (1998) Synthesis of large arrays of well-aligned carbon nanotubes on glass. Journal of Science 282: 1105-1107.
8. Muhammad MAR, Javid I (2011) Production of carbon nanotubes by different routes A Review. JEAS 1: 29-34.
9. Grebenyukov VV, Obratsova ED, Pozharov AS, Arutyunyan NR, Romeikov AA, et al. (2008) Arc-synthesis of single-walled carbon nanotubes in nitrogen atmosphere. Fullerenes, Nanotubes and Carbon Nanostructures 16: 330-334.


\*Corresponding author: Hussein F, College Pharmacy, University of Babylon, Hilla Iraq, Tel: 00964 780 4009236; E-mail: abohasan\_hilla@yahoo.com

Received July 29, 2015; Accepted July 30, 2015; Published August 05, 2015


Citation: Muhammed GJ, Hussein F (2015) Synthesis of Carbon Nanotubes Using Aliphatic Alcohols as a Carbon Source. Chem Sci J 6: e110. doi:10.4172/2150-3494.1000e110

Copyright: © 2015 Muhammed GJ, et al. This is an open-access article distributed under the terms of the Creative Commons Attribution License, which permits unrestricted use, distribution, and reproduction in any medium, provided the original author and source are credited.

10. Takagi DH, Hibino H, Suzuki S, Kobayashi Y, Homma Y (2007) Carbon nanotube growth from semiconductor nanoparticles. Nano Letter 7: 2272-2275.
11. Li YM, Kim W, Zhang YG, Rolandi M, Wang DW, et al. (2001) Growth of single-walled carbon nanotubes from discrete catalytic nanoparticles of various sizes. J Phys Chem B 46: 11424-11431.
12. Cassell AM, Raymakers JA, Kong J, Dai H (1999) Large scale CVD synthesis of single-walled carbon nanotubes. J Phys Chem B 103: 6484.
13. Herrera JE, Resasco DE (2003) Role of CO-W interaction in the selective growth of single-walled carbon nanotubes from CO disproportionation. J Phys Chem B 107: 3738.
14. Warnatz J, Mass U, Dibble RW (2001) Combustion: physical and chemical fundamental, modeling and simulation, experiments, pollutant formation, 3rd (edn) Springer: Berlin p: 257
15. Maruyama S, Kojima R, Miyauchi Y, Chiashi S, Kohno M (2002) Low-temperature synthesis of high-purity single-walled carbon nanotubes from alcohol. Chemical Physics Letters 360: 229-234.
16. Kamil L, Manfred R, Albrecht L, Yulia K, Bernd B, et al. (2010) Magnetic properties of carbon nanotubes with an without catalyst. J Phys Conf Ser 200: 72061-72066.
17. Nikolay D, Sebastian O, Yury G, Eric B (2009) Purification of carbon nanotubes by dynamic oxidation in an air. J Mater Chem 19: 7904-7908.
18. Ameer AA, Abbas JL, Hussein FH (2015) Modification of carbon nanotubes surface using different oxidizing agents. Environmental Analytical Chemistry 2: 1-2.
19. Reich S, Thomsen C, Maultzsch J (2004) Carbon nanotubes: basic concepts and physical properties. Wiley-VCH, Berlin.
20. Mildred SD, Ado J, Mario H, Gene D, Riechiro S (2010) Perspectives on carbon nanotubes and graphene Raman spectroscopy. Nano Letters 10: 751-758.
21. Dikio E, Shooto N, Thema F, Farah A (2013) Raman and TGA study of carbon nanotubes synthesized over Mo/Fe catalyst on aluminium oxide, calcium carbonate and magnesium oxide support. Chem Sci Trans 2: 1160-1173.

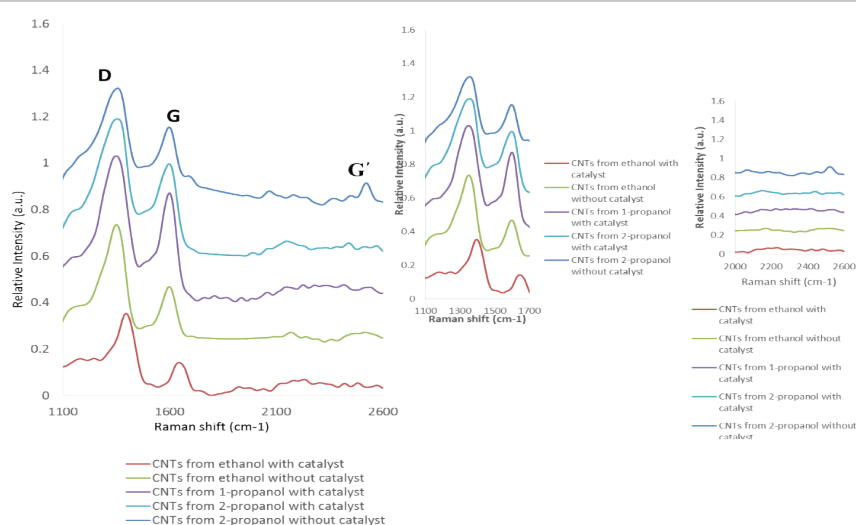

**Figure 1:** Raman spectra of the synthesized CNTs.

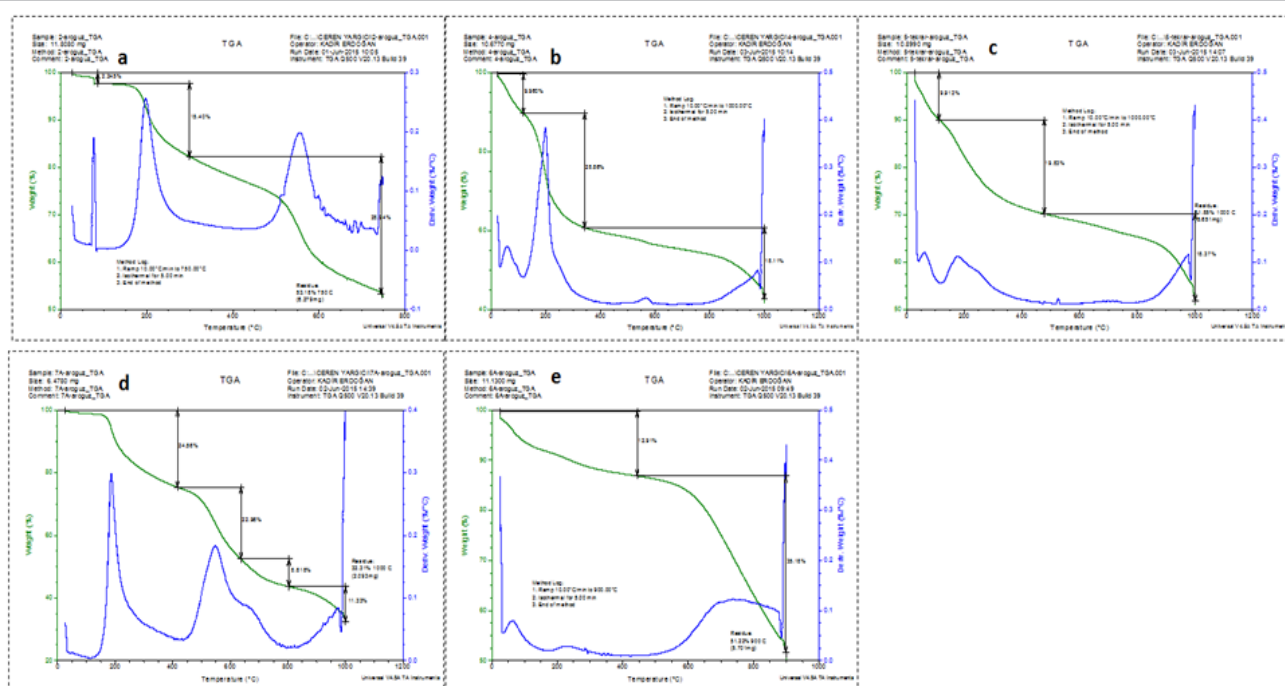

**Figure 2:** TGA of CNTs grown from a) ethanol without catalyst, b) ethanol with catalyst, c) 1-propanol with catalyst, d) 2-propanol without catalyst and e) 2-propanol with catalyst.

Type of carbon source	Weight loss%	The range of temperatures °C	Type of CNTs
Ethanol with catalyst	18.11	380-580	FWCNTs
Ethanol without catalyst	28.94	350-580	MWCNTs with less ratio of FWCNTs
1-Propanol with catalyst	12.33	210-500	mostly FWCNTs
1-Propanol without catalyst	-	-	No yield
2-Propanol with catalyst	35.18	400-900	FWCNTs in addition to MWCNTs
2-Propanol without catalyst	22.96	400-600	MWCNTs and FWCNTs

**Table 1:** The result and conclusions of synthesized CNTs.